
Original Research Article

Experimental evaluation of kinetics and biochemical characteristics of MnO₂ nanoparticles as high throughput peroxidase-mimetic nanomaterials

Saeed Reza Hormozi Jangi

Hormozi Laboratory of Chemistry and Biochemistry, Zabol 9861334367, Iran; saeedrezahormozi@gmail.com

Abstract: Despite the well-known concepts on the intrinsic peroxidase-like activity of MnO₂ nanoparticles, up to date, their biochemical and kinetics characteristics were not investigated, especially, the current information about their performances toward *n*-electron oxidation of 3, 3' -diaminobezedine for producing indamine polymers is on limitation. Therefore, herein, the MnO₂ nanoparticles were synthesized by a simple low-cost co-precipitation method and then characterized by XRD, SEM, and DLS analysis. Besides, their peroxidase-like activity was evaluated upon standard peroxidase enzyme assay, revealing high intrinsic peroxidase-like activity for the as-mentioned MnO₂ nanozymes. Considering their high intrinsic peroxidase-like activity, their optimal biochemical characteristics were quantified by probing the progress of *n*-electron irreversible oxidation of 3, 3' -diaminobezedine in the presence of MnO₂ nanozymes as peroxidase mimics. The maximal activity of the as-mentioned MnO₂ nanoparticles with high intrinsic peroxidase-like activity was observed when the pH and temperature of the reaction media were fixed over 3.0 – 6.0 and 23°C – 25°C, in order, revealing very high pH and thermal stability of the as-prepared nanoparticles. The salt stability of these nanoparticles was also checked using NaCl as model salt, revealing that the nanozymatic activity was stable over a salt concentration as high as 3–7 M. In addition, the affinity constant (K_m) and maximum velocity of the nanozyme-catalyzed oxidation of 3, 3' -diaminobezedine were found to be 1.6 mM and 47 nM sec⁻¹, in turn.

Keywords: MnO₂ nanozyme, Brown-colored polyDAB, pH stability of nanozymes, Thermal stability of nanozymes, Kinetics of nanozymes.

1. Introduction

The fast development of nanoscience and material chemistry has increased interest in researching new and innovative synthesis methods to produce new nanomaterials with unique catalytic activity^[1,2], unique optical properties^[3], high active area^[4], antibacterial properties^[5], and high biocompatibility^[6]. The new field of nanozyme-based catalysis, which has been introduced as an alternative to enzyme-based catalysis, is called nanozyme chemistry. On the other hand, nanozymes are known as nanomaterials with high enzyme-like activity and can be used to simulate enzymatic reactions in harsh environmental conditions (for example, higher temperature or wider pH range)^[7-10]. As previously reported in the literature^[11,12], native enzymes, for instance, native peroxidases or ureases suffer from several disadvantages and drawbacks such as low pH stability, low thermal stability, low recoverability, and no reusability. Commonly, to solve these difficulties and drawbacks of native enzymes, the development of enzyme immobilization protocols has been widely considered in the literature^[13,14]. Although enzyme immobilization can enhance enzyme stability, however, the immobilized enzymes reveal very lower activity than the native enzymes due to the enzyme inactivation during the immobilization process^[15]. Hence to solve these difficulties, the design and development of low-cost nanozymes with higher stability than the native enzymes along with high enzyme-like/mimic activity were considered as an

interesting way for performing enzyme-catalyzed reactions in harsh conditions^[16–18]. Recently, nanozyme-based systems had been used for several applications in the field of catalysis^[19,20], biomedical imaging^[21], tumor therapy^[22,23], and sensing and detection^[24–26].

Manganese dioxide (MnO₂) has been employed for the design and development of different catalytic processes, for example, electro-catalytical, chemical, and photocatalytic processes thanks to its low cost, high catalytic activity, nontoxicity, and high stability compared to other transition metal oxides^[27,28]. However, the MnO₂ nanoparticles are known for their high enzyme-like activity with dual oxidase- and peroxidase-like activity which make them suitable nanozymes for sensing applications^[29–33].

Considering the above-mentioned literature, since, the MnO₂ nanoparticles are well-known as nanozymes with high intrinsic peroxidase-mimic activity, there are several high-impact reports on their applications in the development of analytical and bioanalytical nanozyme-based sensors. Although the peroxidase-like activity of these nanozymes was evaluated in the literature and their potential application for sensing aims was also reported, however, based on our best knowledge, up to date, the biochemical features and kinetics properties of MnO₂ nanoparticles were not evaluated in any report, especially, toward enzyme-mediated oxidation of DAB. Hence, in this study, as a novel idea, the biochemical properties of an enzyme mimic (not a native enzyme) such as pH stability, thermal stability, and salt stability were investigated also, the kinetic features of these nanozymes were calculated toward irreversible oxidation of DAB.

2. Methods

2.1 Synthesis of MnO₂ nanozymes

To synthesize MnO₂ nanozymes, 150 mg KMnO₄ was dissolved in 15 mL of deionized water. Then, 150 μL of 30% hydrogen peroxide and 75 μL of 80% hydrazinium hydroxide were introduced into the solution followed by 5 min stirring. After 2 min, the brown precipitate was collected and then washed five times with deionized water.

2.2 Nanozyme activity assay

A mixture of 40 μL hydrogen peroxide, 0.5 mL of DAB (final concentration of 2.8 mM), and 40 μL of MnO₂-nanozymes (final concentration of 0.015 mg mL⁻¹ in the mixture) was added to 2 mL of 0.4 M acetate buffer (pH = 4.0). After 30 min, the UV-Vis spectra against a reagent blank were recorded at 460 nm. It should be noted that the specific activity of the as-mentioned nanozymes (nM s⁻¹) was calculated using the absorption coefficient of the oxidation product at 460 nm ($\epsilon = 5500 \text{ M}^{-1} \text{ cm}^{-1}$). It is notable that for calculating the nanozyme specific active (nM s⁻¹), the concentration of produced DAB-ox in the reaction media was calculated using $\text{Absorbance} = \epsilon bc$, which ϵ and b are about $5500 \text{ M}^{-1} \text{ cm}^{-1}$ and 1.0 cm, in order, and c is represented to the concentration of DAB-ox. Afterward, the concentration (in nM) was divided by the reaction time to estimate the calculation of the nanozyme specific activity in nM s⁻¹. Thereafter, the relative activity of the MnO₂ nanozymes was calculated using Equation (1)^[34]:

$$\text{Relative activity (\%)} = \text{activity}/(\text{maximum activity}) \times 100 \quad (1)$$

2.3 pH and temperature effect on the nanozymatic activity

The effect of pH on the nanozyme activity was determined by probing their activity over a pH range of 2.0–9.0. Afterward, the relative activity was calculated for each pH using Equation (1), and the plot of activity as a function of pH was used as an index for pH stability measurements. Besides, the thermal stability of the as-mentioned nanozymes was investigated by calculating their activity after incubation at different temperatures for 30 min.

2.4 Salt stability

The nanozyme stability against high salt concentrations as a serious problem of native enzymes was evaluated by recording their nanozymatic activity in reaction media with high salt concentration over 3–7 M. It is notable that NaCl was used as a model salt for this experiment.

2.5 Kinetics studies

The kinetics studies were performed by measuring the activity of the as-mentioned nanozymes as a function of DAB concentrations based on the Michaelis-Menten model. Afterward, the kinetic parameters, V_{\max} and K_m were estimated by using the linear plot of Lineweaver-Burk.

2.6. Instrumentation for material characterization

The UV-Vis measurements were carried out using a CT Chorm Tech UV 3300 spectrophotometer. The SEM and TEM images were recorded using a TESCAN-Vega 3 from TESCAN Company (Czech Republic) and transmission electron microscope (Zeiss, model EL10C), in order. The DLS histogram was provided using a Shimadzu SALD-301V particle size analyzer. The XRD pattern was obtained using a Rigaku D/max-3C (Japan).

3. Results and discussion

3.1 Characterization of the as-prepared MnO₂ nanoparticles

The size and morphological properties of MnO₂ nanoparticles were determined using DLS and scanning electron microscopy imaging methods, respectively. Besides, to explore more precise on the evaluation of the morphology and size of the as-prepared nanoparticles, TEM image of the nanoparticles was also recorded. In addition, the crystalline properties of the as-prepared nanozymes were checked using XRD analysis.

3.1.1 SEM imaging

The morphological properties of the as-mentioned manganese dioxide nanozymes were investigated by SEM imaging method. In this regard, the SEM image of the prepared MnO₂ nanozymes was recorded. The results shown in Figure 1, revealed that the as-prepared MnO₂ nanozymes have uniform and small size particles. However, the SEM image cannot provide any useful information on their size distribution.

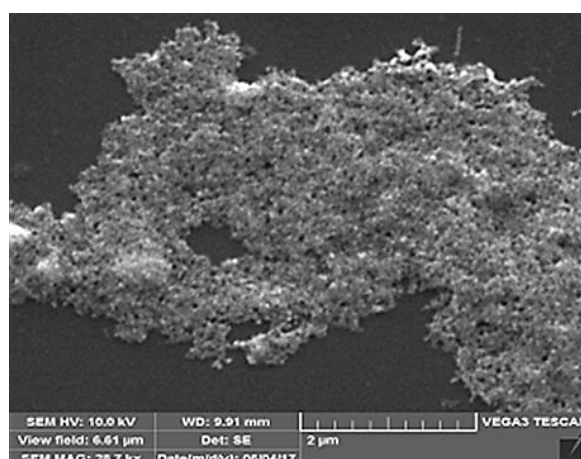


Figure 1 SEM image of the as-prepared MnO₂ nanozymes

3.1.2 TEM imaging

Since the SEM imaging method cannot provide useful and reliable information about the as-mentioned MnO₂ nanozymes, to explore more precise on evaluation of the morphological properties and particle size of these nanozymes, the TEM imaging method was utilized for characterization of the as-prepared MnO₂ nanozymes. The results shown in Figure 2 revealed that the as-prepared MnO₂ nanoparticles have a semi-spherical morphology along with an average size as small as 100 nm.

3.1.3 Particle size estimation using DLS analysis

For estimation of size distribution and accurate and precise calculation of the average size of the as-prepared nanozymes, the DLS analysis was performed using water as solvent. The histogram of the particle size as a function of frequency and undersize is shown in Figure 3. The results shown in Figure 2 revealed that the as-prepared nanozymes have a size distribution over 64 nm–171 nm with an average size of 109 nm.

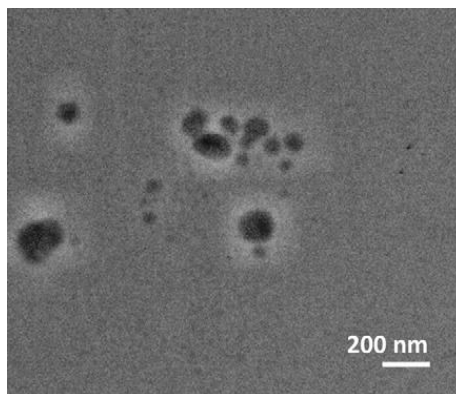


Figure 2 TEM images of the as-synthesized MnO₂ nanoparticles

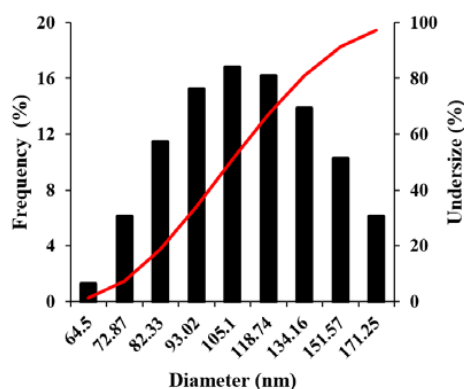


Figure 3 DLS results of the as-prepared MnO₂ nanozymes

3.1.4 Crystalline characteristics

The crystalline properties of the synthesized MnO₂ nanozymes were investigated using XRD analysis. The results of this analysis are shown in Figure 4. As seen in this figure, the results of X-ray diffraction analysis indicate the presence of two characteristic peaks of MnO₂ at the diffraction angles of 23.66 and 60.11 which are assigned to (101) and (312) plans of MnO₂, in order. Notably, the XRD pattern of the as-prepared MnO₂ nanozymes is in good agreement with the reported XRD patterns for MnO₂ nanoparticles^[33].

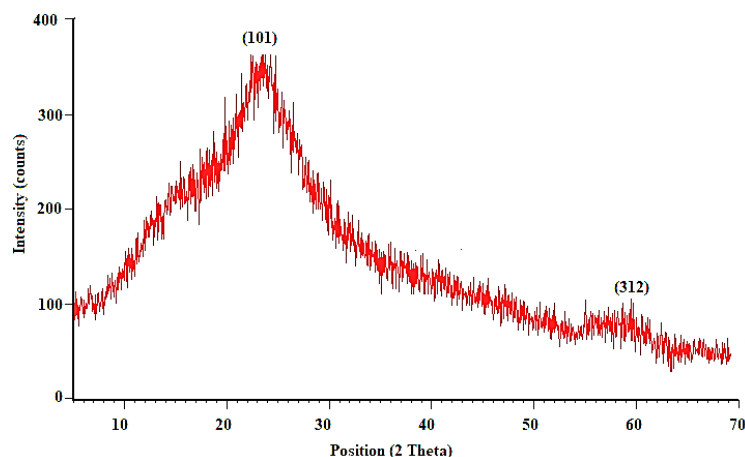


Figure 4 The XRD pattern of the as-prepared MnO₂ nanozymes

3.2 Investigation of nanozymatic behavior of the as-prepared MnO₂ nanoparticles

The peroxidase-like activity of MnO₂ nanoparticles was investigated using DAB as a peroxidase substrate and its brown-colored oxidation product (i.e., polyDAB) as an analytical probe system (Figure 5). As seen in Figure 5, in the presence of DAB, the synthesized MnO₂ nanozymes catalyze the oxidation process of DAB with hydrogen peroxide to form its corresponding brown-colored indamine polymer (polyDAB) with a maximum absorbance at 460 nm. In fact, during the oxidation of DAB, MnO₂ nanozymes act on hydrogen peroxide molecules and produce active hydroxyl radicals^[24,26,31,33]. Then the generated radicals react with DAB molecules to produce the DAB cation (DAB⁺). The DAB⁺ then reacts with a DAB molecule to produce a DAB dimer ((DAB)₂). By proceeding with this cycle, finally, an indamine polymer was produced as the final product of DAB oxidation, as reported^[24,26]. It is notable that the schematic representation of the n-electron irreversible oxidation of DAB over MnO₂ nanoparticles is shown in Scheme 1.


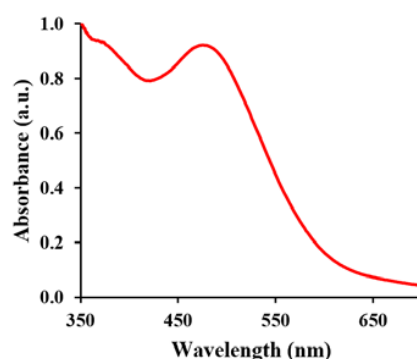


Figure 5 The UV-Visible spectrum of oxidation product of MnO₂ nanozymes-mediated oxidation of DAB

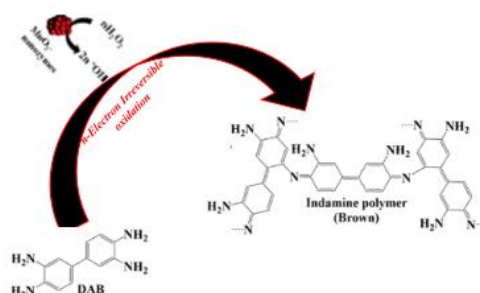

Scheme 1 Schematic representation of DAB oxidation over MnO₂ nanozymes

3.3 pH stability

The effect of pH on the nanozyme activity was determined by probing their activity over a pH range of 2.0–9.0. In fact, this experiment can provide insights into the stability of these nanozymes against environmental pH changes. The results are shown in Figure 6. According to these results, the maximum nanozyme activity of these nanozymes was estimated over a wide pH range of 3.0–6.0. It should be noted that at harsh acidic conditions (pH = 2) and harsh basic conditions (pH = 9.0), the as-mentioned nanozymes saved 82% and 71% of their maximal activity, in turn, pointing to their high pH stability. Compared to the native peroxidase enzymes, the as-prepared MnO₂ nanozymes showed a very wider pH working range. The native peroxidase enzyme reveals a narrow pH range with an optimal pH of 7.0 using pyrogallol as the peroxidase substrate, as reported. It is notable that at pH = 4.0, the native peroxidase shows only about 30% of its maximal activity^[35]. In fact, upon using the as-prepared MnO₂ nanozymes instead of the native peroxidase enzymes, the enzyme-catalyzed reactions can be performed in harsh conditions (for example, pH = 3.0) and in a wide pH range. The activity of the as-prepared nanozymes over pH = 3.0–6.0 was found to be independent of the pH variations which is its significant advantage against the native enzymes.

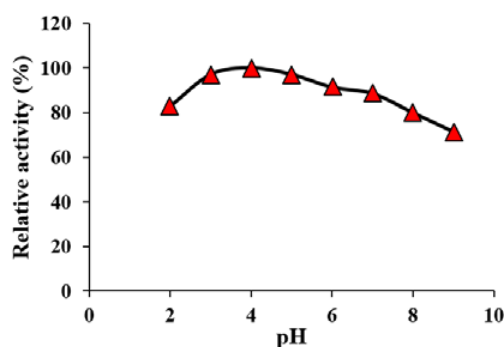


Figure 6 The pH stability of the as-prepared MnO₂ nanozymes

3.4 Thermal stability

The thermal stability of the as-mentioned nanozymes was evaluated by measuring the relative activity of nanozymes over the temperature range of 23°C – 40°C. The results can obtain useful information about both the optimal temperature range of MnO₂ nanozymes and their stability against environmental temperature variations. The results are shown in Figure 7, according to this figure, the maximum nanozyme activity was estimated at a temperature range of 23°C – 25°C and then it was decreased by increasing the temperature. As a significant advantage from a practical point of view, considering the temperature effect on the nanozyme activity, the as-prepared nanozymes can be utilized for proceeding with the peroxidase-mediated reactions in ambient conditions without needing the complex instruments for temperature controlling. In contrast, the native enzyme shows its maximal activity at 50°C, at 30°C and 55°C can save only 40% and 80% of its maximal activity, in order, as reported^[35]. Hence, it can be concluded that the native enzyme is characteristically dependent on the temperature of the reaction media while the as-prepared nanozymes can be applied for catalyzing the enzyme-mediated reaction in ambient temperature (23°C – 25°C).

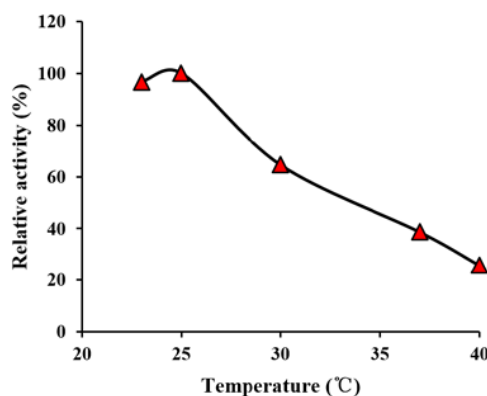


Figure 7 The Thermal stability of the as-prepared MnO₂ nanozymes

3.5 Salt stability

The nanozyme stability against high salt concentrations as a serious problem of native enzymes was evaluated by recording their nanozymatic activity in reaction media with high salt concentration over 3–7 M of NaCl. It is notable that since 1 M is a moderate salt concentration and the native enzymes such as natural proteases are active in this concentration^[36], we checked the salt stability at a very high salt concentration over 3–7 M to prove the higher salt stability of the nanoparticles. The results shown in Figure 8 revealed that the as-mentioned nanozymes can save their maximal activity over a wide range of high salt concentrations over 3–7 M of NaCl. Based on the above results, it can be concluded that the as-prepared MnO₂ nanozymes can be used for catalyzing the peroxidase-mediated oxidation reactions at high salt concentrations without any decrease in catalytic efficiency and nanozymatic activity instead of the unstable native peroxidase.

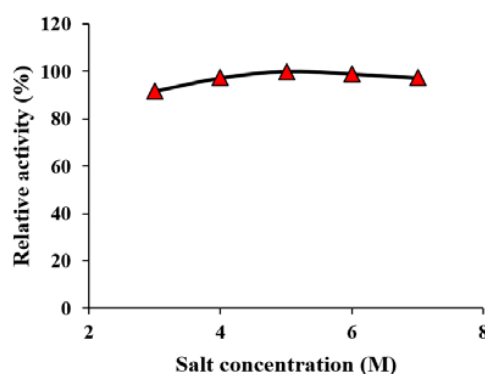


Figure 8 The salt stability of the as-prepared MnO₂ nanozymes

3.6 Kinetics studies

Kinetic studies were carried out to estimate the kinetic parameters (i.e., K_m and V_{max}) of the as-prepared MnO₂ nanozyme as peroxidase-like nanoenzyme toward n -electron irreversible oxidation of 3, 3'-diaminobezidine. It is well known that the V_{max} value reflects the intrinsic properties of the enzyme/nanozyme and is defined as the highest possible rate of the enzyme/nanozyme-catalyzed reaction (i.e., catalytic efficiency) when all enzyme molecules or all nanozyme particles are saturated with the substrate^[34,37]. The higher value of V_{max} is assigned to the higher catalytic efficiency of the enzyme/nanozyme. In contrast, the affinity of the substrate of an enzyme/nanozyme to interact with its active site is represented by the K_m value, the lower values indicate a higher affinity of the substrate for binding to the enzyme/nanozyme^[34,37]. The estimation of the kinetic parameters of MnO₂ nanozymes was performed by measuring the initial velocity of the nanozyme-mediated reaction as a function of the DAB concentration. The Michaelis-Menten saturation curve and the Lineweaver-Burk linear plot for the as-mentioned nanozymes were shown in Figure 9. As seen in Figure 9A, the reaction rate was increased by increasing the DAB concentration and then reached a saturation state after a certain substrate concentration. Besides, Lineweaver-Burk linear plot (Figure 9B) provided a K_m as low as 1.6 mM and a V_{max} as high as 47 nM sec⁻¹ for the MnO₂ nanozymes toward irreversible oxidation of DAB to produce brown-colored polyDAB. Considering the high value of the V_{max} , it can be concluded that the as-prepared nanozymes can catalyze the oxidation reaction of DAB with excellent catalytic efficiency. Besides, the low value of the K_m is pointed to the high affinity of the enzyme-substrate (here, DAB) for binding to the active nodes of the as-prepared nanozymes. It is notable that the kinetic performances of the as-prepared MnO₂ nanozymes were compared with those of the native peroxidase enzyme. As reported in the literature, the V_{max} value of native horseradish peroxidase is about 35 nM sec⁻¹^[38] (enzyme substrate = TMB) which is about 1.4-fold lower than the V_{max} of the MnO₂ nanozymes (enzyme substrate = DAB), exhibited that the catalytic efficiency of the as-prepared nanozymes is higher than that of the native enzyme. Besides, the K_m of native enzyme was found to be as high as 3.6 mM^[38] which is 2.3-fold higher than that of the MnO₂ nanozymes, revealing that the substrate affinity toward MnO₂ nanozymes is 2.3-order higher than the substrate affinity toward native enzyme.

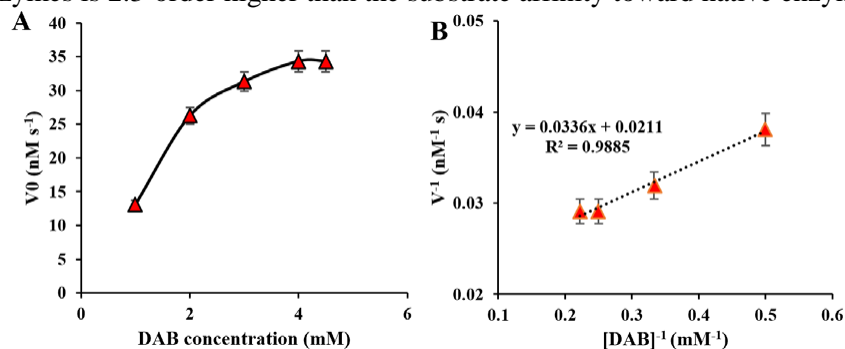


Figure 9 (A) Steady-state Michaelis-Menten saturation curve; (B) Lineweaver-Burk linear plot for the nanozyme-mediated oxidation of DAB over the as-prepared MnO₂ nanozymes

4. Conclusions

Despite the well-known concepts on the intrinsic peroxidase-like activity of MnO₂ nanoparticles, up to date, their biochemical and kinetics characteristics were not investigated, especially, the current information about their performances toward *n*-electron oxidation of 3, 3' -diaminobezedine for producing indamine polymers is on limitation. Therefore, herein, the MnO₂ nanoparticles were synthesized by a simple low-cost co-precipitation method and then characterized by XRD, SEM, and DLS analysis. Besides, their peroxidase-like activity was evaluated upon standard peroxidase enzyme assay, revealing high intrinsic peroxidase-like activity for the as-mentioned MnO₂ nanozymes. Considering their high intrinsic peroxidase-like activity, their optimal biochemical characteristics were quantified by probing the progress of *n*-electron irreversible oxidation of 3, 3' -diaminobezedine in the presence of MnO₂ nanozymes as peroxidase mimics. The maximal activity of the as-mentioned MnO₂ nanoparticles with high intrinsic peroxidase-like activity was observed when the pH and temperature of the reaction media were fixed over 3.0 – 6.0 and 23°C – 25°C, in order, revealing very high pH and thermal stability of the as-prepared nanoparticles. The salt stability of these nanoparticles was also checked using NaCl as model salt, revealing that the nanozymatic activity was stable over a salt concentration as high as 3–7 M. In addition, the affinity constant (K_m) and maximum velocity of the nanozyme-catalyzed oxidation of 3, 3' -diaminobezedine were found to be 1.6 mM and 47 nM sec⁻¹, in turn.

Acknowledgments

The author gratefully thanks the Hormozi Laboratory of Chemistry and Biochemistry for the support of this work.

Conflict of interest

The authors declare no conflict of interest.

References

1. Hormozi Jangi SR, Akhond M. High throughput green reduction of tris (p-nitrophenyl) amine at ambient temperature over homogenous AgNPs as H-transfer catalyst. *Journal of Chemical Sciences* 2020; 132: 110. doi:10.1007/s12039-020-01819-9
2. Hormozi Jangi SR. Low-temperature destructive hydrodechlorination of long-chain chlorinated paraffins to diesel and gasoline range hydrocarbons over a novel low-cost reusable ZSM-5@Al-MCM nanocatalyst: A new approach toward reuse instead of common mineralization. *Chemical Papers* 2023; 77: 4963–4977. doi: 10.1007/s11696-023-02834-z
3. Hormozi Jangi SR, Akhond M. Ultrasensitive label-free enantioselective quantification of D-/L-leucine enantiomers with a novel detection mechanism using an ultra-small high-quantum yield N-doped CDs prepared by a novel highly fast solvent-free method. *Sensors and Actuators B: Chemical* 2021; 339: 129901. doi:10.1016/j.snb.2021.129901
4. He L, Chang C, Xue Q, et al. Bismuth nanoparticles decorated vertically arranged graphene as flexible electrodes for highly efficient detection of Pb(II) ions in water. *Microchemical Journal* 2023; 187: 108433. doi:10.1016/j.microc.2023.108433
5. Zheng Z, Liang W, Lin R, et al. Facile synthesis of zinc indium oxide nanofibers distributed with low content of silver for superior antibacterial activity. *Small Structures* 2023; 4(4): 2200291. doi: 10.1002/sstr.202200291
6. Hormozi Jangi SR. Synthesis and characterization of magnesium-based metal-organic frameworks and investigating the effect of coordination solvent on their biocompatibility. *Chemical Research and Nanomaterials* 2023; 1(4): 1–9.

7. Zhang S, Ruan H, Xin Q, et al. Modulation of the biocatalytic activity and selectivity of CeO₂ nanozymes via atomic doping engineering. *Nanoscale* 2023; 15(9): 4408–4419. doi: 10.1039/D2NR05742E
8. Hormozi Jangi SR, Dehghani Z. Spectrophotometric quantification of hydrogen peroxide utilizing silver nanozyme. *Chemical Research and Nanomaterials* 2023; 2(1): 15–23.
9. Yang D, Wang L, Jia T, et al. Au/Fe₃O₄-based nanozymes with peroxidase-like activity integrated in immunochromatographic strips for highly-sensitive biomarker detection. *Analytical Methods* 2023; 15(5): 663–674. doi: 10.1039/D2AY01815B
10. Akhond M, Hormozi Jangi SR, Barzegar S, Absalan G. Introducing a nanozyme-based sensor for selective and sensitive detection of mercury(II) using its inhibiting effect on production of an indamine polymer through a stable n-electron irreversible system. *Chemical Papers* 2020; 74: 1321–1330. doi: 10.1007/s11696-019-00981-w
11. Hormozi Jangi SR. Introducing a high throughput nanozymatic method for eco-friendly nanozyme-mediated degradation of methylene blue in real water media. *Sustainable Chemical Engineering* 2023; 4(2): 90–99. doi: 10.37256/sce.4220233204
12. Cao L. Immobilised enzymes: Science or art? *Current Opinion in Chemical Biology* 2005; 9(2): 217–226. doi:10.1016/j.cbpa.2005.02.014
13. Homaei AA, Sariri R, Vianello F, Stevanato R. Enzyme immobilization: An update. *Journal of Chemical Biology* 2013; 6(4): 185–205. doi: 10.1007/s12154-013-0102-9
14. Hormozi Jangi SR, Akhond M. High throughput urease immobilization onto a new metal-organic framework called nanosized electroactive quasi-coral-340 (NEQC-340) for water treatment and safe blood cleaning. *Process Biochemistry* 2021; 105: 79–90. doi: 10.1016/j.procbio.2021.03.027
15. Klibanov AM. Enzyme stabilization by immobilization. *Analytical Biochemistry* 1979; 93: 1–25. doi:10.1016/S0003-2697(79)80110-4
16. Hormozi Jangi SR. Determining kinetics parameters of bovine serum albumin-protected gold nanozymes toward different substrates. *Qeios* 2023. doi: 10.32388/07MWBC
17. Hormozi Jangi SR. Effect of daylight and air oxygen on nanozymatic activity of unmodified silver nanoparticles: Shelf-stability. *Qeios* 2023. doi: 10.32388/9RWVYI.3
18. Hormozi Jangi AR, Hormozi Jangi MR, Hormozi Jangi SR. Detection mechanism and classification of design principles of peroxidase mimic based colorimetric sensors: A brief overview. *Chinese Journal of Chemical Engineering* 2020; 28(6): 1492–1503. doi: 10.1016/j.cjche.2020.01.020
19. Bittencourt GA, de Souza Vandenberghe LP, Martínez-Burgos WJ, et al. Emerging contaminants bioremediation by enzyme and nanozyme-based processes—A review. *iScience* 2023; 26(6): 106785. doi: 10.1016/j.isci.2023.106785
20. Ahmadi-Leilakouhi B, Hormozi Jangi SR, Khorshidi A. Introducing a novel photo-induced nanozymatic method for high throughput reusable biodegradation of organic dyes. *Chemical Papers* 2023; 77(2): 1033–1046. doi:10.1007/s11696-022-02542-0
21. Liu C, Fan W, Cheng WX, et al. Red emissive carbon dot superoxide dismutase nanozyme for bioimaging and ameliorating acute lung injury. *Advanced Functional Materials* 2023; 33(19): 2213856. doi: 10.1002/adfm.202213856
22. Zeng X, Ruan Y, Chen Q, et al. Biocatalytic cascade in tumor microenvironment with a Fe₂O₃/Au hybrid nanozyme for synergistic treatment of triple negative breast cancer. *Chemical Engineering Journal* 2023; 452, Part 2: 138422. doi: 10.1016/j.cej.2022.138422
23. Han J, Yoon J. Supramolecular nanozyme-based cancer catalytic therapy. *ACS Applied Bio Materials* 2020; 3(11): 7344–7351. doi: 10.1021/acsabm.0c01127
24. Hormozi Jangi SR, Akhond M. Synthesis and characterization of a novel metal-organic framework called nanosized electroactive quasi-coral-340 (NEQC-340) and its application for constructing a reusable

- nanozyme-based sensor for selective and sensitive glutathione quantification. *Microchemical Journal* 2020; 158: 105328. doi:10.1016/j.microc.2020.105328
25. Yu R, Wang R, Wang Z, et al. Applications of DNA-nanozyme-based sensors. *Analyst* 2021; 146(4): 1127–1141. doi: 10.1039/D0AN02368J
 26. Hormozi Jangi SR, Davoudli HK, Delshad Y, et al. A novel and reusable multinanozyme system for sensitive and selective quantification of hydrogen peroxide and highly efficient degradation of organic dye. *Surfaces and Interfaces* 2020; 21: 100771. doi: 10.1016/j.surfin.2020.100771
 27. Xia HY, Li BY, Zhao Y, et al. Nanoarchitected manganese dioxide (MnO₂)-based assemblies for biomedicine. *Coordination Chemistry Reviews* 2022; 464: 214540. doi: 10.1016/j.ccr.2022.214540
 28. Tang Y, Zheng S, Cao S, et al. Advances in the application of manganese dioxide and its composites as electrocatalysts for the oxygen evolution reaction. *Journal of Materials Chemistry A* 2020; 8(36): 18492–18514. doi: 10.1039/D0TA05985D
 29. Wu J, Yang Q, Li Q, et al. Two-dimensional MnO₂ nanozyme-mediated homogeneous electrochemical detection of organophosphate pesticides without the interference of H₂O₂ and color. *Analytical Chemistry* 2021; 93(8): 4084–4091. doi: 10.1021/acs.analchem.0c05257
 30. Zou N, Wei X, Zong Z, et al. Preparation of manganese dioxide nanozyme as catalyst for electrochemical sensing of hydrogen peroxide. *International Journal of Electrochemical Science* 2021; 16(3): 210324. doi: 10.20964/2021.03.47
 31. Hormozi Jangi SR, Akhond M, Absalan G. A novel selective and sensitive multinanozyme colorimetric method for glutathione detection by using an indamine polymer. *Analytica Chimica Acta* 2020; 1127: 1–8. doi: 10.1016/j.aca.2020.06.012
 32. Yin Z, Ji Q, Wu D, et al. H₂O₂-responsive gold nanoclusters @ mesoporous silica @ manganese dioxide nanozyme for “off/on” modulation and enhancement of magnetic resonance imaging and photodynamic therapy. *ACS Applied Materials & Interfaces* 2021; 13(13): 14928–14937. doi: 10.1021/acsami.1c00430
 33. Hormozi Jangi SR, Akhond M, Absalan G. A field-applicable colorimetric assay for notorious explosive triacetone triperoxide through nanozyme-catalyzed irreversible oxidation of 3, 3' -diaminobenzidine. *Microchimica Acta* 2020; 187(8): 431. doi: 10.1007/s00604-020-04409-1
 34. Hormozi Jangi SR, Akhond M, Dehghani Z. High throughput covalent immobilization process for improvement of shelf-life, operational cycles, relative activity in organic media and enzymatic kinetics of urease and its application for urea removal from water samples. *Process Biochemistry* 2020; 90: 102–112. doi: 10.1016/j.procbio.2019.11.001
 35. Temoçin Z, İnal M, Gökgöz M, Yiğitoğlu M. Immobilization of horseradish peroxidase on electrospun poly (vinyl alcohol)-polyacrylamide blend nanofiber membrane and its use in the conversion of phenol. *Polymer Bulletin* 2018; 75: 1843–1865. doi: 10.1007/s00289-017-2129-5
 36. Ruginescu R, Enache M, Popescu O, et al. Characterization of some salt-tolerant bacterial hydrolases with potential utility in cultural heritage bio-cleaning. *Microorganisms* 2022; 10(3): 644. doi: 10.3390/microorganisms10030644
 37. Hormozi Jangi SR, Akhond M. Introducing a covalent thiol-based protected immobilized acetylcholinesterase with enhanced enzymatic performances for biosynthesis of esters. *Process Biochemistry* 2022; 120: 138–155. doi: 10.1016/j.procbio.2022.06.004
 38. Hormozi Jangi SR, Dehghani Z. Kinetics and biochemical characterization of silver nanozymes and investigating impact of storage conditions on their activity and shelf-life. *Chemical Research and Nanomaterials* 2023; 1(4): 25–33.